



PHOTOCATALYTIC DEGRADATION OF INDIGO CARMINE DYE ON COMBUSTION SYNTHESIZED $MgZrO_3$ CATALYST UNDER SOLAR LIGHT IRRADIATION

C.R.Hatwar^{a*}, P.S.Deshpande^d, S.Dafare^e, L.R.Hatwar^c, C.B.Talwatkar^b, R.S.Bhavsar^a

^{a*} Department of Chemistry, Institute of Science, Nagpur-440 001 (M.S.) India

^a Department of Chemistry, Institute of Science, Nagpur-440 001 (M.S.) India

^b Department of Chemistry, S.M.M.College of Science, Nagpur-440 009 (M.S.) India

^c Department of Physics, K.R.Pandav Mahavidyalaya, Nagpur -440009 (M.S.) India

^d Department of Chemistry, Sevadal Mahila Mahavidyalaya, Nagpur-440 009 (M.S.) India

^e Department of Chemistry, J.M.Patel College of Arts, Commerce & Science, Bhandara -441904 (M.S.) India

ABSTRACT

The Magnesium Zirconate ($MgZrO_3$) catalyst was prepared by solution combustion synthesis method and extensively characterized by XRD, SEM, TGA, DTA, Reflectance spectroscopy, BET surface area and powder density. An indigo Carmine (IC) dye was used as model pollutants to study its photocatalytic degradation under solar light irradiation. The degradation of IC was investigated by COD analyzer and UV-Visible spectroscopy. The influences of catalyst amount, initial dye concentration, pH of the reaction solution and irradiation time were investigated. Results of characterization confirmed the formation of $MgZrO_3$ catalyst. Recycling experiments confirmed the relative stability of the catalyst.

Keywords: Photocatalysis; Degradation; SEM; $MgZrO_3$; Combustion Synthesis;

1. Introduction


Environmental protection, which requires strictly sustainable development to avoid jeopardizing current natural resources, is gradually becoming a matter of major social concern. Every day, increasingly tough legislation is being imposed with regard to effluent discharge (Martínez-Huitle, Rodrigo, Sirés, Scialdone, 2015). The textile effluent is highly colored; its emancipation in the environment is a considerable source of non aesthetic pollution and encumbers light penetration, thus disturbing aquatic life (Barka.,

Assabbane, Nounah, Ait Ichou, 2008; Neelamegam, Baskaran, Dhanasekar, Viruthagiri, 2004). Waste water is commonly characterized by its strong color, high chemical oxygen demand (COD), variable pH, total dissolved solids (TDS) content and low biodegradability, implying the presence of refractory organic matter (Korbati, Tanyolac, 2008). Especially azo dyes, which are non-biodegradable, toxic and potentially carcinogenic in nature, are widely used (Sun, Wang, Sun, Sun, Sun, Qiao, 2006). These azo dyes were found to have immense hazardous effects on human health and environment (Akbari-Fakhrabadi, Saravanan, Jamshidijam, Mangalaraja, Gracia, 2015). Hence removal of these dyes from effluents is a major environmental problem because conventional physicochemical and biological treatment methods are ineffective for decolorization and degradation. Many chemical and physical techniques including adsorption, coagulation, precipitation, filtration, electro dialysis, membrane separation and oxidation have been used efficiently for removal of dye pollutants (Ozacar, Sengil, 2003). However, they are non destructive, since they transfer organic compounds from water to another phase, thus causing secondary pollution (Lam, Sin, Abdullah, Mohamed, 2012). Recently, Advanced oxidation processes (AOP's) in which heterogeneous semiconductor photocatalysis emerge as a promising destructive method, leading to mineralization of organic pollutants from wastewater (Ahmed,

Rasul, Brown, Hashib, 2011; Vo, Thi, Kim, Kim, 2014; Saravanan, Khan, Gupta, Mosquera, Gracia, Narayanan, Stephen, 2015; Khan, Ansari, Khan, Ansari, Min, Cho, 2015; Hisaindee, Meetani, Rauf, 2013). Photocatalysis is based on the principle that when a semiconductor is exposed to a light source with appropriate wavelength, the electrons from the valence band are promoted to the conduction band leaving positive holes in the valence band. The generated electron-hole pair moves to the

semiconductor surface and reacts with organic pollutants degrading them into non hazardous by-products (Lavand, Malghe, 2015).

The consumption of Indigo carmine dye causes permanent injury to cornea and conjunctiva, it is carcinogenic and can lead to reproductive, developmental, neuron and acute toxicity (Jenkins, 1978). It also causes gastrointestinal irritations with nausea, vomiting and diarrhea (Ng, Datta, Kirimli, 1976; Ikeda, Sannohe, Araki, Inutsuka, 1982)

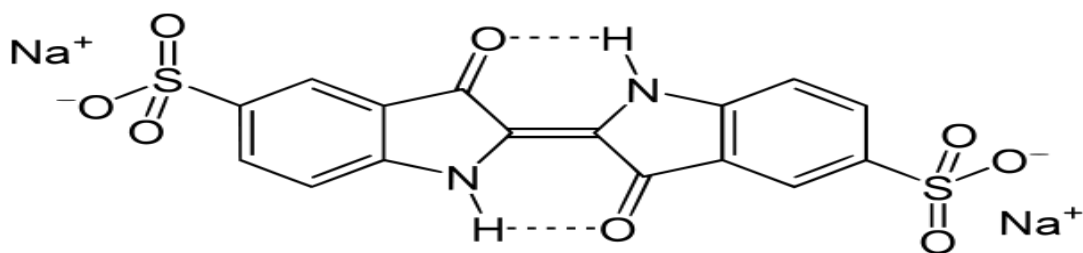

Indigo Carmine (IC), Molecular weight: 466.36 g mol⁻¹

Various attempts have been made for the removal of indigo carmine dye from water and wastewater (Zakaria, Ashtoukhy, 2013; Zhu, H., Jiang, R., Xiao, L., Chang, Y., Guan, Y., Li, X., Zeng, G. 2009). Apart from adsorption over chitin and chitosan (Prado, Torres, Faria, Dias, (2004) and charcoal from extracted residue of coffee beans (Nakamura, Hirata, Kawasaki, Tanada, Tamura, Nakahori, 2003), electrochemical (Fernandez-Sanchez, Costa-Garcia, 2000), biological (Abadulla, Tzanov, Costa, Robra, Cavaco-Paulo, Giibitz, 2000) and photochemical (Hachem, Bocquillon, Zahraa, Bouchy, 2001) techniques have also been explored.

In present work, the MgZrO₃ catalyst was synthesized by combustion synthesis method in which fuel and oxidizer were taken in stoichiometric proportion and characterized in detail. IC dye was selected as object pollutant. Indoor solar light was used as irradiation source. Different factors for degradation were investigated. The results obtained in this study could provide fundamental information for the treatment of waste water containing organic dyes. Literature survey reveals that the MgZrO₃ not used earlier

for removal of Indigo carmine dye from water and waste water.

2. Experimental

Commercially available Indigo carmine and Zirconium nitrate were purchased from LOBA Chemie company (Mumbai, India). Magnesium nitrate, Ammonium nitrate, glycine and urea were purchased from Merck (India). All chemicals used as received without further purification. All solutions were prepared in double distilled water. Dilute hydrochloric acid and dilute sodium hydroxide in proper amount was used to adjust the suitable pH value.

2.1 Synthesis of MgZrO₃ catalyst

Magnesium Zirconate was synthesized by solution combustion synthesis method in which Magnesium nitrate and Zirconium nitrate were used as oxidizer and glycine, urea and ammonium nitrate were used as fuels in stoichiometric proportion (i.e. O/F = 1). The redox mixture was dissolved in a cylindrical pyrex dish of approximately 250 ml capacity. The amount of oxidizer and fuel were taken in such a way that the desired product i.e. MgZrO₃ obtained was 5 g. Dish containing the solution was introduced into muffle furnace preheated at 400 °C. Mixture boils, foams and ignites to burn, yielding voluminous and foamy MgZrO₃

which occupies the entire volume of the dish. The time required for completion of reaction was less than 15 min. Finally, it was calcined at 800 °C for 2 hr in air to obtain pure form of MgZrO₃.

2.2 Physicochemical characterization of MgZrO₃ catalyst

The crystallinity and phase identification of the powder was determined by powder XRD using Philips PW-1700 diffractometer with Ni filtered CuK α radiation. A reflectance spectrum was recorded on GBC Cintra 10e (Australia) spectrophotometer. Surface area measurements were done using nitrogen gas adsorption multipoint Brunquer-Emmett-Teller (BET) method on Micromeritics ASAP 2010 model, assuming a cross sectional area of 0.162 nm² for nitrogen molecule. Powder density was measured using pycnometer with xylene as the liquid medium. The diameter of the primary particle was calculated from superficial area using following equation:

$$DBET = 6/SBET \cdot \rho$$

Where SBET is the superficial area (m² g⁻¹) measured by BET analyses; ρ , the density of powders (g cm⁻³); and DBET, the diameter of the produced particle. SEM micrograph was recorded on JEOL 6380A electron probe analyzer instrument after coating the sample with gold for evaluation of particle morphology.

2.3 Photodegradation study of Indigo carmine dye

A glass cylindrical tube having 250 ml capacity was used for irradiation of model dye solution. Air was allowed to pass into dye solution using

aerator. A known amount of dye solution (100 cm³) and MgZrO₃ catalyst was taken in cylinder. Solution was irradiated under indoor solar light. At given irradiation time intervals, 10 ml of the suspension were collected, centrifuged and filtered to separate the photocatalyst particles. After each irradiation the IC dye concentration was measured by UV-Visible Spectrophotometer (UV-1800, Simadzu, Japan) at 600 nm and COD analysis were carried out on UNIPHOS India make COD analyzer, before that, sample were digested for 2 hr at 150 °C in UNIPHOS COD digester. The degradation and removal of COD were studied by varying different parameters such as catalyst amount, initial concentration of dye, pH of the dye solution and irradiation time.

2.4 Regeneration of catalyst

Regeneration process of used catalysts was carried out after irradiation of dyes. The used catalyst was separated from solution. Washed with small amount of distilled water and kept in muffle furnace at 600 °C for 2 hr. Also stability of MgZrO₃ in acid and alkali was studied by keeping it in 1M HCl and 1M NaOH for 24 hr. Experiments was carried out for IC dye with regenerated catalyst at its optimized parameters.

3. Results & Discussion

3.1 Characterization of MgZrO₃

Fig. 1 shows the XRD pattern of MgZrO₃. An excellent match is found with standard XRD pattern of MgZrO₃. It is observed that a single phase, crystalline nature has been formed.

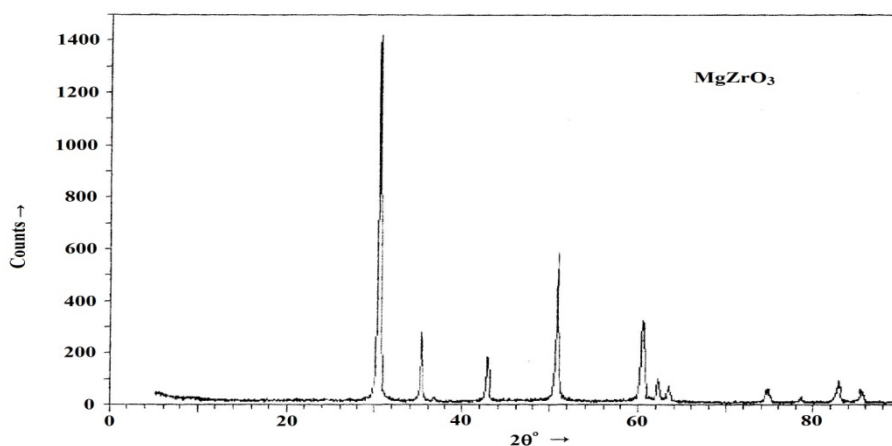


Fig. 1. X-ray diffraction pattern of MgZrO₃

DTA and TGA curves of MgZrO_3 (Fig. 2) shows the compound is almost stable with no weight loss. DTA graph of MgZrO_3 shows two endothermic and one exothermic peaks. The first endothermic break at 308.7°C reaches a

peak at 361.2°C and end at 411.7°C . The second endothermic curve begins at 722.7°C reaches a peak at 737.8°C end at 754.9°C and The third exothermic curve begins at 850.8°C reaches a peak at 890.9°C end at 909.9°C .

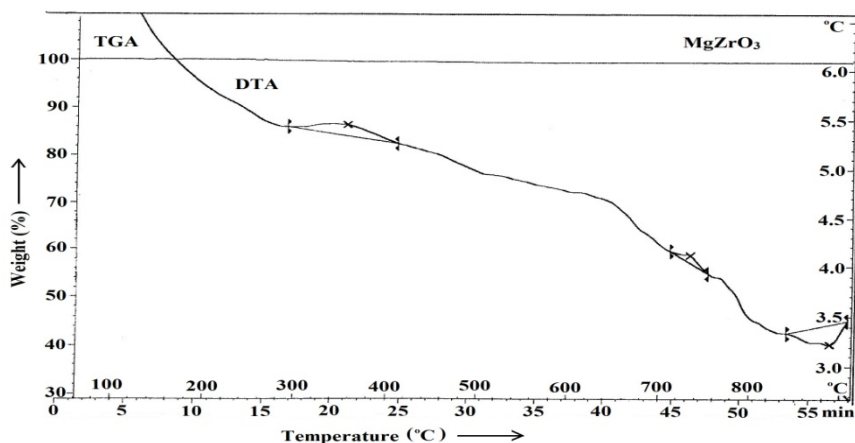


Fig. 2. Thermogram of TGA and DTA of MgZrO_3

The diffuse reflectance spectra is an efficient tool for the determination of energy band gap of MgZrO_3 . The band gap energy of MgZrO_3 was found to be 3.92 eV. BET surface area was found to be $56.1571\text{ m}^2\text{g}^{-1}$. Powder density was found to be 2.07 g cm^{-3} . The average particle diameter was found to be 52 nm which was calculated from BET surface area measurement and density value.

The morphology of MgZrO_3 samples was investigated by scanning electron

microscopy (SEM) with JEOL 6380A microscope. SEM image of MgZrO_3 powders calcined at 800°C is shown in Fig. 3. The SEM image clearly indicates the high homogeneity of the MgZrO_3 powders.

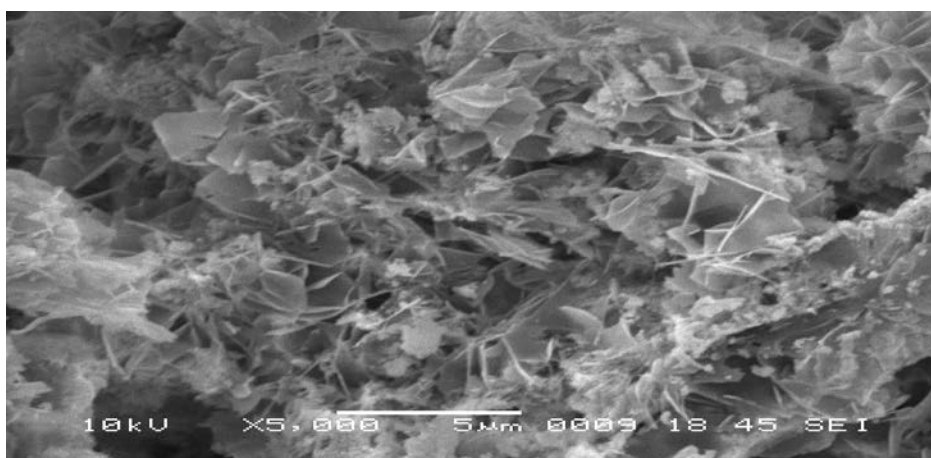


Fig. 3. Scanning electron microscopy image of MgZrO_3

3.2 Photocatalytic degradation studies

3.2.1 Effect of pH

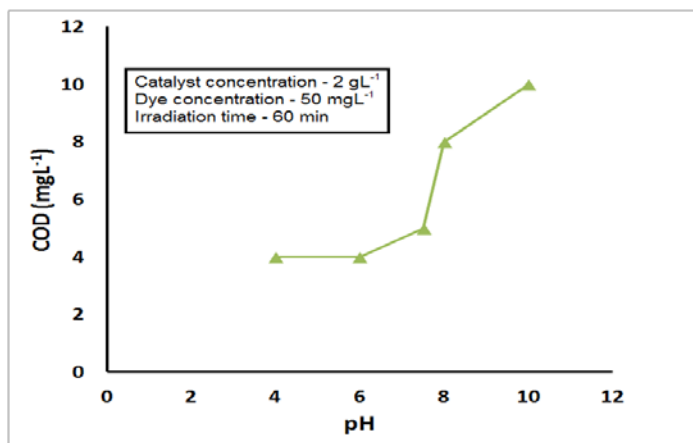


Fig.4. Effect of pH on COD removal of IC dye

3.2.2 Effect of catalyst concentration

The effect of catalyst concentration on the degradation of IC was investigated employing different concentration of MgZrO_3 ranging from 1 to 3.5 gL^{-1} shown in Fig. 5. As expected the COD of dye solution was found to decrease with increase in catalyst concentration up to 2.5 gL^{-1} , further increase in catalyst concentration found no change in COD. The increase in the efficiency seems to be due to the effective surface area of catalyst and the absorption of light. At lower catalyst loading, the absorption of light controlled the photocatalytic process due to the limited catalyst surface area. However, as the catalyst loading increased, an increase in the active sites of MgZrO_3 is obtained. The large amount of photons adsorbed

and the amount of dyes adsorbed on the MgZrO_3 surface improved the photocatalytic degradation. When the MgZrO_3 loading was high, nevertheless, owing to an increase in the particles aggregation, the surface that absorbed the photons is not increasing in a geometrical ratio. In addition, the number of active sites on the MgZrO_3 surface also decreased because of the decrease in light penetration due to light scattering effect. With an increase in the turbidity of the suspension and shrinking of the effective photoactivated volume of suspension, the degradation rate is decreased. The integration of these two reasons resulted in a reduced performance of photocatalytic activity rather than the linearly increase with the overloaded catalyst.

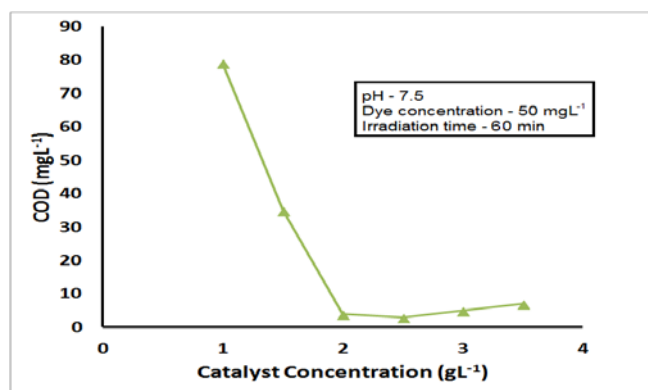


Fig. 5. Effect of catalyst concentration on COD removal of IC dye

3.2.3 Effect of dye concentration

It is important both from a mechanistic and from an application point of view to study the dependence of the photocatalytic reaction rate on the dye concentration. The initial dye

concentration can influence the extent of photocatalytic reaction rate at the surface of catalyst. Hence the effect of dye concentration on degradation of IC was studied at varying concentration from 25 mgL^{-1} to 200 mgL^{-1}

keeping other parameters constant (Fig. 6). The COD of dye solution increase with increase in dye concentration from 25 mgL^{-1} to 200 mgL^{-1} . The initial dye concentration dependence of the degradation rate of dye can be realized by the fact that the photocatalytic reaction occurs on MgZrO_3 particles as well as in solution. On the surface of MgZrO_3 particles, the reaction occurs between the OH^\bullet radicals generated at the active OH^- sites and dye molecule from the solution.

In addition, a significant amount of light may also be absorbed by the dye molecules rather than the MgZrO_3 at a higher initial dye concentration. This condition can be ascribed to the increase in the initial concentration which led to less photons reaching on the MgZrO_3 surface and resulted in a slower production of OH^\bullet radicals. Consequently, the degradation rate is decreased.

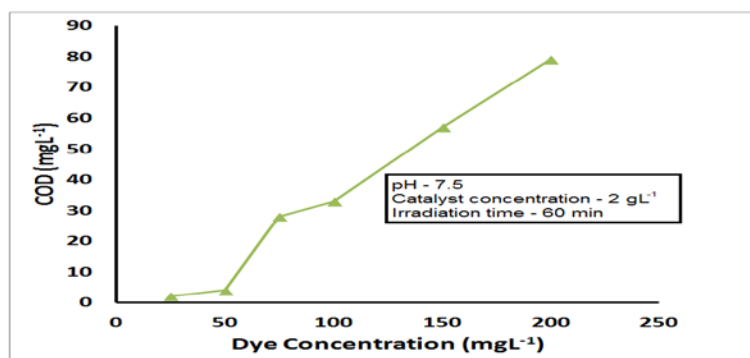


Fig.6. Effect of dye concentration on COD removal of IC dye

3.2.4 Effect of irradiation time

The effect of irradiation time on degradation of IC dyes was investigated and same is revealed in Fig.7. The irradiation time was varied from

15 min to 120 min keeping other parameters constant. It was observed that the maximum quantity of IC dye was degraded up to 60 - 90 min.

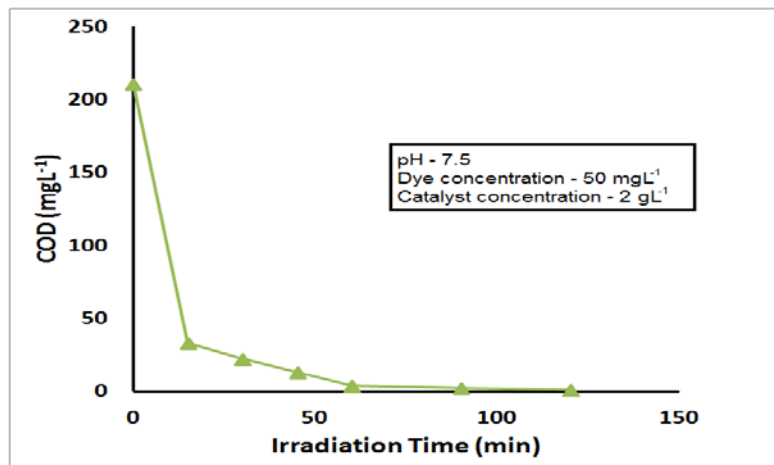


Fig. 7. Effect of irradiation time on COD removal of IC dye

3.2.5 Degradation and Decolorization

The UV-visible spectra of the original IC solution and degraded dye solution are presented in Fig. 8. The full spectrum scanning pattern showed extremely obvious difference. No peak was detected in analyzed wavelength range at the end of 90min of reaction time in

presence of MgZrO_3 (2.5 gL^{-1}) under indoor solar light irradiation indicating complete destruction of IC dye. As a result, both an appropriate light source and catalyst are essential for photocatalytic decolorization and degradation of the IC dye on MgZrO_3 to occur

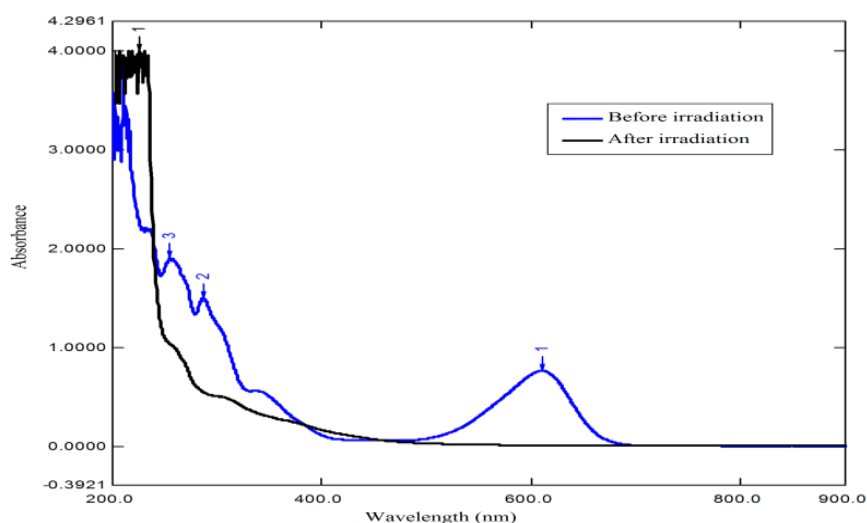


Fig. 8. UV-visible spectrum of IC dye solution before and after irradiation

3.2.6 Catalyst regeneration

The regeneration of catalysts was carried out with used catalyst. The degradation of dyes was studied using these regenerated photocatalysts at optimized parameters and it was found that almost equal degradation has been observed.

4. Conclusion

Magnesium Zirconate was successfully synthesized by using combustion synthesis method at 400 °C within 15 min. time interval. Magnesium Zirconate was found to be efficient photocatalyst for photodegradation of Indigo carmine dye, nearly 98 percent COD removal and 97% color removal was observed in 60 min using indoor solar light as a source of irradiation. MgZrO₃ can be regenerated and reused effectively and degradation efficiency from observation was found to be nearly similar to that of original MgZrO₃.

REFERENCES

1. Martínez-Huitle, C. A., Rodrigo, M.A., Sirés, I., Scialdone, O. (2015). Single and coupled electrochemical processes and reactors for the abatement of organic water pollutants: A critical review, *Chem. Rev.*, 115 (24), 13362–13407.
2. Barka, N., Assabbane, A., Nounah, A., Ait Ichou, Y. (2008). Photocatalytic degradation of indigo carmine in aqueous solution by TiO₂-coated non-woven fibres, *J. Hazard. Mater.* 152, 1054-1059.
3. Neelamegam, R., Baskaran, V., Dhanasekar, R., Viruthagiri, T. (2004). Decolourization of synthetic dyes using rice straw attached pleurotus ostreatus, *Ind. J. Chem. Tech.* 11, 622-625.
4. Korbahti, B.K., Tanyolac, A. (2008). Electrochemical treatment of simulated textile wastewater with industrial components and Levafix Blue CA reactive dye: Optimization through response surface methodology, *J. Hazard. Mater.* 151, 422-431.
5. Sun, J., Wang, X., Sun, J., Sun, R., Sun, S., Qiao, L. (2006). Photocatalytic degradation and kinetics of orange G using nano-sized Sn (IV)/ TiO₂/AC photocatalyst, *J. Mole. Catal. A: Chem.* 260, 241-246.
6. Akbari-Fakhrabadi, A., Saravanan, R., Jamshidijam, M., Mangalaraja, R.V., Gracia, M.A. (2015). Preparation of nanosized yttrium doped CeO₂ catalyst used for photocatalytic application, *J. Saudi Chem. Soc.* 19(5), 505-510.

7. Ozacar, M., Sengil, I.A. (2003). Adsorption of reactive dyes on calcined alunite from aqueous solution, *J. Hazard. Mater.* 98, 211-224.
8. Lam, S-M., Sin, J-C., Abdullah, A.Z., Mohamed, A.R. (2012). Degradation of wastewaters containing organic dyes photocatalysed by zinc oxide: a review, *Des. Water. Treat.* 41, 131-169.
9. Ahmed, S., Rasul, M.G., Brown, R., Hashib, M.A. (2011). Influence of parameters on the heterogeneous photocatalytic degradation of pesticides and phenolic contaminants in wastewater: a short review, *J. Environ. Manag.* 92, 311-330.
10. Vo, V., Thi, T.P.T., Kim, H.Y., Kim, S.J. (2014). Facile post synthesis and photocatalytic activity of N-doped ZnO-SBA-15, *J. Phys. Chem. Solids* 75, 403-409.
11. Saravanan, R., Khan, M.M., Gupta, V.K., Mosquera, E., Gracia, F., Narayanan, V., Stephen, A. (2015). ZnO/Ag/Mn₂O₃ nanocomposite for visible light induced industrial textile effluent degradation, uric acid and ascorbic acid sensing and antimicrobial activity, *RSC Adv.* 5, 34645-34651.
12. Khan, M.M., Ansari, S.A., Khan, M.E., Ansari, M.O., Min, B.K., Cho, M.H. (2015). Visible light-induced enhanced photoelectrochemical and photocatalytic studies of gold decorated SnO₂ nanostructures, *New J. Chem.* 39, 2758-2766.
13. Hisaindee, S., Meetani, M.A., Rauf, M.A. (2013). Application of LC-MS to the analysis of advanced oxidation process (AOP) degradation of dye product and reaction mechanisms, *Tren. Analy. Chem.* 49, 31-44.
14. Lavand, A.B., Malghe, Y.S. (2015). Visible light photocatalytic degradation of 4-chlorophenol using C/ZnO/CdS nanocomposite, *J. Saudi. Chem. Soc.* 19, 471-478.
15. Jenkins, C.L. (1978). *Arch. Environ. Health* 40(5), 7-12.
16. Ng, T.Y., Datta, T.D., Kirimli, B.I. (1976). Reaction to indigo carmine, *J. Urol.* 116, 132-133.
17. Ikeda, K., Sannohe, Y., Araki, S., Inutsuka, S. 1982. Intra-arterial dye method with vasomotors (PIAD method) applied for the Endoscopic Diagnosis of gastri cancer and the side effects of indigo carmine, *Endoscopy.* 14(4), 119-123.
18. Zakaria, El. S., Ashtoukhy, El. (2013). Removal of Indigo Carmine Dye from Synthetic Wastewater by Electrochemical Oxidation in a New Cell with Horizontally Oriented Electrodes, *Int. J. Electrochem. Sci.* 8, 846-858.
19. Zhu, H., Jiang, R., Xiao, L., Chang, Y., Guan, Y., Li, X., Zeng, G. (2009). Photocatalytic decolorization and degradation of Congo Red on innovative crosslinked chitosan/nano-CdS composite catalyst under visible light irradiation, *J. Hazard. Mater.* 169, 933-940.
20. Prado, A.G.S., Torres, J.D., Faria, E.A., Dias, S.C.L. (2004). Comparative adsorption studies of indigo carmine dye on chitin and chitosan, *J. Colloid Interface Sci.* 277 (1), 43-47.
21. Nakamura, T., Hirata, M., Kawasaki, N., Tanada, S., Tamura, T., Nakahori, Y. (2003). Decolorization of Indigo Carmine by Charcoal from Extracted Residue of Coffee Beans, *J. Environ. Sci. Health A* 38(3), 555-562.
22. Fernandez-Sanchez, C., Costa-Garcia, A. (2000). Voltammetric studies of indigo adsorbed on pre-treated carbon paste electrodes, *Electrochem. Commun.* 2(11), 776-781.
23. Abadulla, E., Tzanov, T., Costa, S., Robra, K.H., Cavaco-Paulo, A., Giibitz, G.M. (2000). Decolorization and Detoxification of Textile Dyes with a Laccase from *Trametes hirsute*, *App. Environ. Microb.* 66(8), 3357-3362.
24. Hachem, C., Bocquillon, F., Zahraa, O., Bouchy, M. (2001). Decolourization of textile industry wastewater by the photocatalytic degradation process, *Dyes Pigments* 49(2), 117-125.